

Underlying Pairing States in Cuprate Superconductors

Wei-Min Zhang

Department of Physics, National Cheng Kung University, Tainan, Taiwan 701, Republic of China
(February 7, 2008)

In this Letter, we develop a microscopic theory to describe the close proximity between the insulating antiferromagnetic (AF) order and the d -wave superconducting (dSC) order in cuprates. We show that the cuprate ground states form a configuration of coherent pairing states consisting of extended singlet Cooper pairs and triplet π pairs, which can simultaneously describe AF and dSC orders.

PACS numbers: 74.20.-z, 74.20.Mn, 74.25.Ha, 71.10.-w

Discovery of high- T_c superconductivity in copper-oxides [1] reveals very attractive, but also extremely complicated, new phenomena in strongly correlated electron systems [2]. One of the most striking phenomena is the close proximity between the Mott insulating antiferromagnetic (AF) order and the d -wave superconducting (dSC) order. Theorists have tried various different mechanisms, such as the theory of resonating valence bond (RVB) states of singlet pairs introduced by Anderson a decade ago [3] and the SO(5) unified theory of AF and dSC order parameters proposed by S. C. Zhang recently [4], to explain this metal-insulator transition. However, a microscopic description of the AF to dSC transition has not yet been completed.

It is believed that the underlying dynamics of strongly correlated electrons in cuprate superconductors can be modeled by the one-band 2D Hubbard model or the $t - J$ model [3,5]. Unfortunately, the $t - J$ model itself is difficult to solve. Anderson's RVB state is a Mott insulating singlet at half-filling. However, it does not have AF ordering. In Zhang's SO(5) theory, AF order parameters are a part of the building blocks. However, near half-filling, this AF order may not be Mott insulating, due to the lack of the constraint of no-doubly occupied sites which can destroy the SO(5) group structure. Gauge theories later developed in terms of slave bosons in the charge spin separation scenario of RVB states [6], and various microscopic tests of the SO(5) theory made in the past year [7], certainly provided deeper understanding to high T_c superconductivity, but the mechanism concerning the AF to dSC transition remains unsolved.

Most likely, the low energy degrees of freedom in cuprates should still be dominated by electron pairs, although pairing structures may be different from the singlet Cooper pairs in BCS theory or the triplet pairs in He³ superfluid theory. Experiments confirmed the existence of the $d_{x^2-y^2}$ pairing symmetry in cuprate superconductors. However, this does not imply that these electron pairs must all be spin singlet pairs, even though cuprate ground states are total spin singlet. Indeed, with d -wave singlet pairs alone, it is difficult to make a manifestation of the AF to dSC transition.

In this Letter, we start with an insulating AF ordering of the undoped (half-filling) cuprate compound to ex-

plore how superconductivity emerges in doped cuprates. We find that insulating AF and dSC orders can be simultaneously described by a configuration of coherent pairing states consisting of extended singlet Cooper pairs and triplet π pairs. At half-filling, this configuration is dominated by the insulating AF ordering arisen from the mixing of singlet and triplet pairs. Upon doping with holes the d -wave pairing gap appears, and above a certain level cuprates become superconducting. In this description, the nature of no-doubly occupied sites and the present of triplet π pairs play an important role.

We shall begin with the formation of electron pairs in strongly correlated systems. The square lattice structure of layered copper-oxides allows us to restrict the problem in the reduced (half) first Brillouin zone in momentum space. Then the cuprate ground states may be obtained by projecting out all states of no-doubly occupied sites from the following generalized pairing state $|\Phi\rangle$:

$$|\Phi\rangle = \prod_{\mathbf{k}} \exp \left\{ \eta_1(\mathbf{k}) c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger + \eta_2(\mathbf{k}) c_{\mathbf{k}+\mathbf{Q}\uparrow}^\dagger c_{-\mathbf{k}+\mathbf{Q}\downarrow}^\dagger + \eta_3(\mathbf{k}) c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}+\mathbf{Q}\downarrow}^\dagger + \eta_4(\mathbf{k}) c_{\mathbf{k}\downarrow}^\dagger c_{-\mathbf{k}+\mathbf{Q}\uparrow}^\dagger + \eta_5(\mathbf{k}) c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}+\mathbf{Q}\uparrow}^\dagger + \eta_6(\mathbf{k}) c_{\mathbf{k}\downarrow}^\dagger c_{-\mathbf{k}+\mathbf{Q}\downarrow}^\dagger - \text{H.c.} \right\} |0\rangle. \quad (1)$$

where the complex parameters $\eta_i(\mathbf{k})$ are generally *link-dependent* pairing wave functions. The parity symmetry in the $x - y$ plane requires $\eta_i(\mathbf{k}) = \eta_i(-\mathbf{k})$. In the generalized coherent state theory [8], $|\Phi\rangle$ is a product (over $\mathbf{k}$) of the local SO(8)/U(4) coherent pairing states [9].

In fact, Eq. (1) is also a multi-pair generalization of BCS pairing states or RVB states (after projection). Explicitly, we may rewrite $\eta_1(\mathbf{k}) = \eta_s(\mathbf{k}) + \eta_d(\mathbf{k})$, $\eta_2(\mathbf{k}) = \eta_s(\mathbf{k}) - \eta_d(\mathbf{k})$, $\eta_3(\mathbf{k}) = \eta_{\pi_0}(\mathbf{k}) + \eta_\eta(\mathbf{k})$, $\eta_4(\mathbf{k}) = \eta_{\pi_0}(\mathbf{k}) - \eta_\eta(\mathbf{k})$, and $\eta_5(\mathbf{k}) = \eta_{\pi_+}(\mathbf{k})$, $\eta_6(\mathbf{k}) = \eta_{\pi_-}(\mathbf{k})$. Then, Eq. (1) consists of all electron pairs concerned in the study of superconductivity. These are the ordinary s -wave Cooper pairs given by the $\eta_s(\mathbf{k})$ term, the extended (i.e. valence bond) singlet Cooper pairs by the $\eta_d(\mathbf{k})$ terms [including the extended s -wave, d -wave and $s + id$ pairs in terms of $\eta_d(\mathbf{k}) = \eta_{\mathbf{k}}^{es} \gamma(\mathbf{k})$, $\eta_{\mathbf{k}}^d d(\mathbf{k})$ and $\eta_{\mathbf{k}}^{s+id} (\cos k_x + i \cos k_y)$ respectively], the quasi-spin η pairs by the $\eta_\eta(\mathbf{k})$ term which generate quasispin SU(2) transformations, the singlet p -wave pairs [if one lets

$\eta_\eta(\mathbf{k}) = \eta_{\mathbf{k}}^p(\sin k_x \pm \sin k_y)$, and finally the triplet π pairs by $\eta_{\pi_i}(\mathbf{k}) = \eta_{\mathbf{k}}^{\pi_i} d(\mathbf{k})$, here $\gamma(\mathbf{k}) = \cos k_x + \cos k_y$ and $d(\mathbf{k}) = \cos k_x - \cos k_y$.

At half filling, without any loss of generality, we set $\eta_s(\mathbf{k}) = \eta_\eta(\mathbf{k}) = 0$, i.e., $\eta_1(\mathbf{k}) = -\eta_2(\mathbf{k})$ and $\eta_3(\mathbf{k}) = \eta_4(\mathbf{k})$ for the AF ordered phase. In addition, the cuprate ground states must also be spin singlet due to the spin rotational symmetry which implies $\langle \Phi | S^\alpha | \Phi \rangle = 0$. This can be satisfied if $\eta_5(\mathbf{k}) = -\eta_6(\mathbf{k})$. These restrictions on pairing wave functions can be justified by explicitly calculating the AF order parameters from (1):

$$m_z = -\frac{1}{2N} \sum_{\mathbf{k}}' \left[(z_{1\mathbf{k}} - z_{2\mathbf{k}})(z_{3\mathbf{k}}^* + z_{4\mathbf{k}}^*) + \text{H.c.} \right],$$

$$m_+ = m_- = \frac{1}{2N} \sum_{\mathbf{k}}' \left[(z_{1\mathbf{k}} - z_{2\mathbf{k}})(z_{5\mathbf{k}}^* - z_{6\mathbf{k}}^*) + \text{H.c.} \right], \quad (2)$$

where m_z and $m_\pm$ are the average staggered magnetizations in the z direction and the $x-y$ plane, respectively, N is the total number of lattice sites, and the parameters $z_{i\mathbf{k}}$ are elements of the 4×4 block matrix $Z_{\mathbf{k}}$ in the canonical Bogoliubov transformations induced by (1): $Z_{\mathbf{k}} = \eta \sin \sqrt{\eta^\dagger \eta} / \sqrt{\eta^\dagger \eta}$ with

$$\eta(\mathbf{k}) = \frac{1}{2} \begin{bmatrix} 0 & \eta_1(\mathbf{k}) & \eta_5(\mathbf{k}) & \eta_3(\mathbf{k}) \\ -\eta_1(\mathbf{k}) & 0 & \eta_4(\mathbf{k}) & \eta_6(\mathbf{k}) \\ -\eta_5(\mathbf{k}) & -\eta_4(\mathbf{k}) & 0 & \eta_2(\mathbf{k}) \\ -\eta_3(\mathbf{k}) & -\eta_6(\mathbf{k}) & -\eta_2(\mathbf{k}) & 0 \end{bmatrix}. \quad (3)$$

The undoped ground state maximizes the staggered magnetization which corresponds to

$$z_{1\mathbf{k}} = -z_{2\mathbf{k}} = z_{d\mathbf{k}}, \quad z_{3\mathbf{k}} = z_{4\mathbf{k}}, \quad z_{5\mathbf{k}} = -z_{6\mathbf{k}}. \quad (4)$$

This is the same as letting $\eta_1(\mathbf{k}) = -\eta_2(\mathbf{k})$, $\eta_3(\mathbf{k}) = \eta_4(\mathbf{k})$ and $\eta_5(\mathbf{k}) = -\eta_6(\mathbf{k})$. These restrictions on the pairing wave functions are also necessary for the manifestation of the extended (including d -wave) pairing symmetry of valence bonds, because Eq. (4) implies $\eta_i(\mathbf{k} + \mathbf{Q}) = -\eta_i(\mathbf{k})$.

In the above calculation, we have not imposed the constraint of no-doubly occupied sites. However, the result can be further verified under this constraint. Here, instead of using Gutzwiller projector P_G to remove doubly occupied sites from $|\Phi\rangle$, it is equivalent to require that $|\Phi\rangle$ must satisfy the constraint $\langle \Phi | \sum_i (n_{i\uparrow} n_{i\downarrow}) | \Phi \rangle = 0$, where summation to i is over the lattice sites. This is because the operator $n_{i\uparrow} n_{i\downarrow}$ is positive definite. In the mean-field approximation of (1), we obtain the global constraint:

$$\frac{n^2}{4N^2} - m_s^2 + |\Delta_s|^2 + |\Delta_\eta|^2 = 0, \quad (5)$$

where $n = \langle \Phi | \hat{n} | \Phi \rangle$ is the total electron number:

$$n = 2 \sum_{\mathbf{k}}' \sum_{i=1}^6 |z_{i\mathbf{k}}|^2 = N(1 - \delta) \quad (6)$$

and δ the fractional doping of holes, m_s denotes the magnitude of the long-range AF order parameter determined

from (2) by $m_s^2 = m_z^2 + m_+ m_-$, and Δ_s and Δ_η are averaged order parameters of the ordinary s -wave Cooper pairs and the quasispin η pairs which *vanish* under (4): $\Delta_s = \Delta_\eta = 0$. Then, Eq. (5) reduces to

$$m_s^2 = \frac{n^2}{4N^2}. \quad (7)$$

At half-filling ($\delta = 0$), it gives $m_s = 0.5$ which is the same result as in Néel states.

Furthermore, because of the spin rotational symmetry, without loss of generality we can define $z_{3\mathbf{k}} = z_{\pi\mathbf{k}} \cos 2\theta_{\mathbf{k}}$ and $z_{5\mathbf{k}} = z_{\pi\mathbf{k}} \sin 2\theta_{\mathbf{k}}$. Thus, from (7), we find that $\theta_{\mathbf{k}} = \theta$ for all $\mathbf{k}$ [10] and

$$z_{\pi\mathbf{k}} = z_{d\mathbf{k}} \quad \text{or} \quad z_{\pi\mathbf{k}} = -z_{d\mathbf{k}}. \quad (8)$$

This indicates that under the constraint of no-doubly occupied sites, the extended singlet Cooper pairs and triplet π pairs in $|\Phi\rangle$ have *equal occupied probabilities*. Also, Eqs. (2) and (6) reduces to

$$m_s = \frac{4}{N} \sum_{\mathbf{k}}' |z_{d\mathbf{k}}|^2, \quad n = 8 \sum_{\mathbf{k}}' |z_{d\mathbf{k}}|^2 = N(1 - \delta) \quad (9)$$

and $m_z = m_s \cos 2\theta$, $m_+ = m_- = m_s \sin 2\theta$. Here m_s and n can be written only in terms of the singlet pairing wave function $z_{d\mathbf{k}}$ because of the constraint of no-doubly occupied sites (8). At half-filling, electrons are uniformly distributed. Then Eq. (9) gives

$$|z_{d\mathbf{k}}| = 1/2. \quad (10)$$

This is indeed the local constraint of no-doubly occupied sites at half-filling. One can show that $\langle \Phi | (\hat{n} - n)^2 | \Phi \rangle = 0$ under (8) and (10).

The above rigorous results are derived only from the kinematics of the coherent pairing state $|\Phi\rangle$. Dynamically, we may determine the ground state from the $t-J$ model. The t -term is a hopping Hamiltonian $H_t = \sum_{\mathbf{k}, \sigma} \varepsilon(\mathbf{k}) c_{\mathbf{k}\sigma}^\dagger c_{\mathbf{k}\sigma}$, where $\varepsilon(\mathbf{k}) = -2t(\cos k_x + \cos k_y)$. Its expectation value is

$$\langle H_t \rangle = 2 \sum_{\mathbf{k}}' \varepsilon(\mathbf{k}) (|z_{1\mathbf{k}}|^2 - |z_{2\mathbf{k}}|^2) \quad (11)$$

which vanishes by (4), as expected from the constraint of no-doubly occupied sites at half-filling. Under the restriction (4), the expectation value of the J -term [$H_J = J \sum_{\langle i,j \rangle} (S_i \cdot S_j - \frac{1}{4} n_i n_j)$] is given by

$$\frac{\langle H_J \rangle}{JN} = - \left(|\Delta_d|^2 + |\Delta_{es}|^2 + 2m_s^2 + \frac{n^2}{2N^2} \right), \quad (12)$$

where the averaged d -wave pairing order parameter

$$\Delta_d = \frac{1}{N} \sum_{\mathbf{k}}' d(\mathbf{k}) \left(z_{\mathbf{k}}^+ w_{\mathbf{k}}^+ + z_{\mathbf{k}}^- w_{\mathbf{k}}^- \right)$$

$$= \frac{2}{N} \sum_{\mathbf{k}}' d(\mathbf{k}) z_{d\mathbf{k}} \sqrt{1 - 4|z_{d\mathbf{k}}|^2}, \quad (13)$$

and the extended s -wave pairing order parameter Δ_{es} has the same form as (13) by replacing $d(\mathbf{k})$ with $\gamma(\mathbf{k})$. The parameters $z_{\mathbf{k}}^{\pm} = z_{d\mathbf{k}} \pm z_{\pi\mathbf{k}}$ and $w_{\mathbf{k}}^{\pm} = \sqrt{1 - |z_{\mathbf{k}}^{\pm}|^2}$. Note that although it can be written in terms of $z_{d\mathbf{k}}$ in the second equality of (13) [because of the constraint (8)], Δ_d receives contributions from both the singlet and triplet pairs. As a result, Δ_d behaves very different from that in pure singlet pair states. At half-filling, (10) ensures $\Delta_d = \Delta_{es} = 0$. Then $\langle H_J \rangle = -JN$ which again gives the same result as in Néel states.

These results are very remarkable. It shows that under constraints (4) and (8), the coherent pairing state $|\Phi\rangle$ is insulating AF ordering at half-filling. It consists of extended singlet Cooper pairs and triplet π pairs with equal pair numbers. The singlet pairs are indeed Anderson's RVB pairs [3], while the triplet π pairs are the π operators of Demler and Zhang [11]. Both the AF and dSC order parameters are functions of extended pairing wave functions (including the extended s -wave, d -wave and $s + id$ pairing functions [12]) of singlets and triplets. However, because of the constraint of no-doubly occupied sites, the pairing order parameter vanishes while the AF order parameter is the same as in Néel states.

Meanwhile, although the configuration of coherent pairing states contains the same AF properties as the Néel configuration, these two configurations are different. Electrons in Néel states are not paired and Néel configuration itself is only valid for half-filling. However, $|\Phi\rangle$ is defined for any doping and it is built with extended (valence bond) pairs. Thus, $|\Phi\rangle$ provides a natural path to explore how cuprates undergo the transition from an insulating AF order to a dSC order after dopings.

Upon doping with holes, it is commonly believed that hoppings rapidly destroy the AF ordering. Eq. (11) shows that the lowest energy gained from the t -hopping corresponds to $z_{2\mathbf{k}} = 0$, which reduces AF order parameter by a half, as shown by (2). Apparently this is a nice result as expected from hopping dynamics. However, $z_{2\mathbf{k}} = 0$ leads to a non-vanishing Δ_s . A non-vanishing Δ_s enhances the AF order parameter m_s by the constraint (5), which is contrary to (2) for $z_{2\mathbf{k}} = 0$. Indeed, the ordinary Cooper pairs are on-site pairs which are excluded by the constraint of no-doubly occupied sites. In terms of energy scales, the on-site repulsive Coulomb interaction is much stronger than hoppings, a non-vanishing Δ_s contributes a large positive Coulomb energy to the ground states, which is certainly unfavored. Indeed, any net contribution from the t -hopping in mean-field theory requires $|z_{1\mathbf{k}}|^2 \neq |z_{2\mathbf{k}}|^2$, which will break the extended singlet pairing symmetry. Hence, doped ground states must still be restricted by (4).

As a result, after dopings, $|\Phi\rangle$ still consists of the extended singlet Cooper pairs and triplet π pairs. All equations derived above are still valid except for (10). Eq. (9) shows that the AF order parameter m_s is decreased lin-

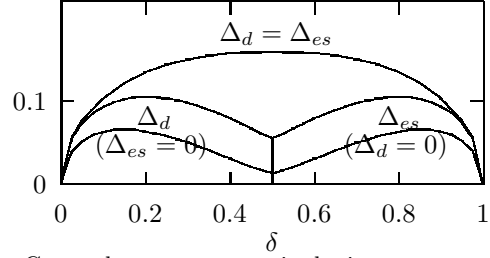


FIG. 1. Gap order parameters via dopings at zero temperature. The (top) solid line is for $t'/J = 0$, and the middle and bottom lines are for $t'/J = 0.2$ and 0.3 , respectively.

early with doping δ . By further including the quantum fluctuation of spin-wave excitations, m_s is suppressed from 0.5 to 0.3 at half-filling [13], and will be suppressed as well upon dopings. While, the pairing order parameter Δ_d [given by Eq. (13)] is zero at half-filling. Then it is increased after dopings so that superconducting states will emerge at a certain level of dopings.

To be more explicit, we may take again the $t - J$ model as an example. When all electrons in ground states are paired, the t -term vanishes by the pairing symmetry $z_{1\mathbf{k}} = -z_{2\mathbf{k}}$ for any doing. However, the next order hopping (t' -term) has a non-zero expectation value in $|\Phi\rangle$. The ground states can be determined by minimizing the $t' - J$ Hamiltonian, which leads to $z_{d\mathbf{k}} \rightarrow |z_{d\mathbf{k}}|e^{i\phi}$ and the gap equation at zero-temperature,

$$\Delta_{\mathbf{k}} = \frac{1}{N} \sum_{\mathbf{k}'} V_{\mathbf{k}\mathbf{k}'} \frac{\Delta_{\mathbf{k}'}}{2E_{\mathbf{k}'}} \quad (14)$$

where $\Delta_{\mathbf{k}} \equiv \Delta_d d(\mathbf{k}) + \Delta_{es} \gamma(\mathbf{k})$, $V_{\mathbf{k}\mathbf{k}'} = J[d(\mathbf{k})d(\mathbf{k}') + \gamma(\mathbf{k})\gamma(\mathbf{k}')] + \gamma(\mathbf{k})\gamma(\mathbf{k}')$ and $E_{\mathbf{k}} = \{J^2 \Delta_{\mathbf{k}}^2 + [\varepsilon(\mathbf{k}) - \mu - 2(1 - \delta)J]^2\}^{1/2}$ with $\varepsilon(\mathbf{k}) = -4t' \cos k_x \cos k_y$. The fixed electron number gives $-\frac{2}{N} \sum_{\mathbf{k}} \frac{\varepsilon(\mathbf{k}) - \mu - 2(1 - \delta)J}{E_{\mathbf{k}}} = 1 - 2\delta$, and μ is the chemical potential.

The solutions of (14) show that the d -wave gap order parameter appears after dopings for $\delta < 0.5$ with maximum peak $\Delta_d \simeq 0.07 \sim 0.10$ at $\delta \simeq 0.15 \sim 0.20$ (the typical optimal doping region) for $t'/J = 0.30 \sim 0.20$. This is in good agreement with the experimental observations of d -wave superconducting states in cuprates. It is also striking that the extended s -wave superconducting states only emerge in overdoped region of $\delta > 0.5$. The separation of the d -wave states in optimal dopings from the extended s -wave states in overdopings is controlled by the t' -term. Here t' must be positive. For a negative t' , the ordering of Δ_d and Δ_{es} in terms of δ will be exchanged. If we let $t' = 0$, then $\Delta_d = \Delta_{es}$ which have the maximum value at doping $\delta = 0.5$. This corresponds to the symmetry limit of Zhang's SO(5) theory [see (12)], although generally the pairing wave functions determined here do not form a rigorous global SO(5) group structure [14]. The numerical results are plotted in Fig. 1.

The above results are very different from the d -wave

singlet pair theory. The d -wave singlet pair states correspond to the special case of (1) with $\eta_1(\mathbf{k}) = -\eta_2(\mathbf{k}) = \eta_d(\mathbf{k})$ and other $\eta_i(\mathbf{k}) = 0$ ($i=3$ to 6). Then from (2), (6) and (13), we have

$$m_s = 0, \quad n = 4 \sum_{\mathbf{k}}' |z_{d\mathbf{k}}|^2 = N(1 - \delta)$$

$$\Delta_d = \frac{2}{N} \sum_{\mathbf{k}}' d(\mathbf{k}) z_{d\mathbf{k}} \sqrt{1 - |z_{d\mathbf{k}}|^2}. \quad (15)$$

Hence, with singlet pairs alone, no AF order exists. The order parameter Δ_d has a maximum value near half-filling ($z_{1\mathbf{k}} \simeq \sqrt{1/2}$), then it is slowly decreased with dopings [12]. Of course, here the constraint of no-doubly occupied sites cannot be imposed analytically by (7) so that auxiliary-boson variables must be introduced [6].

Formally, (15) and (13) show that the magnitude of Δ_d in pure singlet pair states is about twice of that in mixed states of singlet and triplet pairs. In other words, pure singlet pair states have lower gap energies than mixed pair states. However, mixed pair states maximize the AF energy which cannot be taken into account in pure singlet pair states [see Eq. (12) in the $t-J$ model, for an example]. Because of the AF energy, mixed pair states have indeed a lower ground state energy than pure singlet pair states in the mean-field theory.

Summarizing the above discussions, we show that underlying pairing states undergoing an insulating AF to dSC transition can be determined by the coherent state $|\Phi\rangle$ of extended (valence bond) singlet Cooper pairs mixed with triplet π pairs. These coherent pairing states are unconventional, and can be regarded as a nontrivial generalization of Anderson's singlet pair RVB states. Advantage of the coherent pairing state $|\Phi\rangle$ is that it contains an intrinsic AF order which is Mott insulating at and near half-filling, while in optimal dopings, it has the d -wave SC order. Therefore, it can *microscopically* unify the insulating AF and dSC orders in the same configuration. This is for the first time to analytically show that a pairing state can simultaneously describe both the AF order and the dSC order. Dynamically, we show that due to the extended singlet pairing symmetry, the contribution from the t -hopping is, surprisingly, cancelled in (classical) ground states. The exchange interaction (J -term) manifests a symmetry limit of Zhang's SO(5) theory. While, the insulating AF to dSC transition under dopings that is comparable with experimental observations can be determined by the next nearest-neighbor hoppings (with a positive but weak t' hopping).

Furthermore, the canonical transformation structure of (1) generates a quasiparticle picture, which allows us to easily determine normal state properties of cuprates as well as the phase diagram of high T_c superconductivity in the $T - \delta$ plane [15]. Also note that cuprate ground states determined here by minimization are classical states. In these classical ground states, $z_{d\mathbf{k}} \rightarrow |z_{d\mathbf{k}}|e^{i\phi}$ and $\theta_{\mathbf{k}} \rightarrow \theta$ so that the configuration manifests the global

$SU_{\text{spin}}(2) \times U_{\text{gauge}}(1)$ degeneracy. This $SU(2) \times U(1)$ symmetry will be spontaneously broken at quantum level. The quantum fluctuations of $z_{d\mathbf{k}}$ and $\theta_{\mathbf{k}}$ describe pairing excitations and spin-wave excitations (Goldstone modes) which further lower energies of the ground states over all dopings. Therefore, these fluctuations play a very important role in the determination of dynamical properties of electrons in cuprates. A typical evidence is the AF magnetic ordering which is too strong in classical ground states [see (7)]. However, it can be largely suppressed (and should be cancelled in optimal dopings) by the quantum fluctuation of spin-wave excitations [13]. In separate publications [16], based on the generalized coherent state theory [8] we shall use $|\Phi\rangle$ to develop a theory of quantum fluctuations to detail these features, and then to describe dynamical and thermal properties of high T_c superconductivity in cuprates.

I wish to thank T. K. Lee, J. X. Li, Q. Niu and C. S. Ting for many useful discussions.

-
- [1] J. G. Bednora and K. A. Müller, Z. Phys. **B64**, 189 (1986); C. W. Chu *et al.*, Phys. Rev. Lett. **58**, 405 (1987).
 - [2] E. Dagotto, Rev. Mod. Phys. **66**, 763 (1994).
 - [3] P. W. Anderson, Science **235**, 1196 (1987).
 - [4] S. C. Zhang, Science, **275**, 1089 (1997).
 - [5] F. C. Zhang and T. M. Rice, Phys. Rev. **B37**, 3759 (1988).
 - [6] I. Affleck, et al, Phys. Rev. **B38**, 745 (1988); M. U. Ubbens and P. A. Lee, *ibid*, **B46**, 8434 (1992); X. G. Wen and P. A. Lee, Phys. Rev. Lett. **76**, 503 (1996).
 - [7] D. Scalapino et al, Phys. Rev. **B58**, 443 (1998), R. Eder, et al, *ibid* **B57**, 13781 (1998); S. Rabello, et al, Phys. Rev. Lett. **80**, 3586 (1998).
 - [8] W. M. Zhang, D. H. Feng and R. Gilmore, Rev. Mod. Phys. **62**, 867 (1990)
 - [9] W. M. Zhang, D. H. Feng and J. N. Ginocchio, Phys. Rev. Lett. **59**, 2032 (1987).
 - [10] This is a manifestation of the global spin rotational symmetry. Specifying the value of θ spontaneously breaks the spin rotational symmetry, which leads to the gapless spin-wave excitations.
 - [11] E. Demler and S. C. Zhang, Phys. Rev. Lett. **75**, 4126 (1995); Nature, **369**, 733 (1998).
 - [12] G. Kotliar, Phys. Rev. **B37**, 3664 (1988)
 - [13] S. Chakravarty, B. I. Halperin and D. R. Nelson, Phys. Rev. Lett. **60**, 1057 (1988).
 - [14] C. L. Henley, Phys. Rev. Lett. **80**, 3590 (1998).
 - [15] W. M. Zhang, "Quasiparticles in Cuprate Superconductors", to be published.
 - [16] W. M. Zhang, "Quantum Fluctuations of Coherent Pairs in High T_c Superconductivity", to be published.